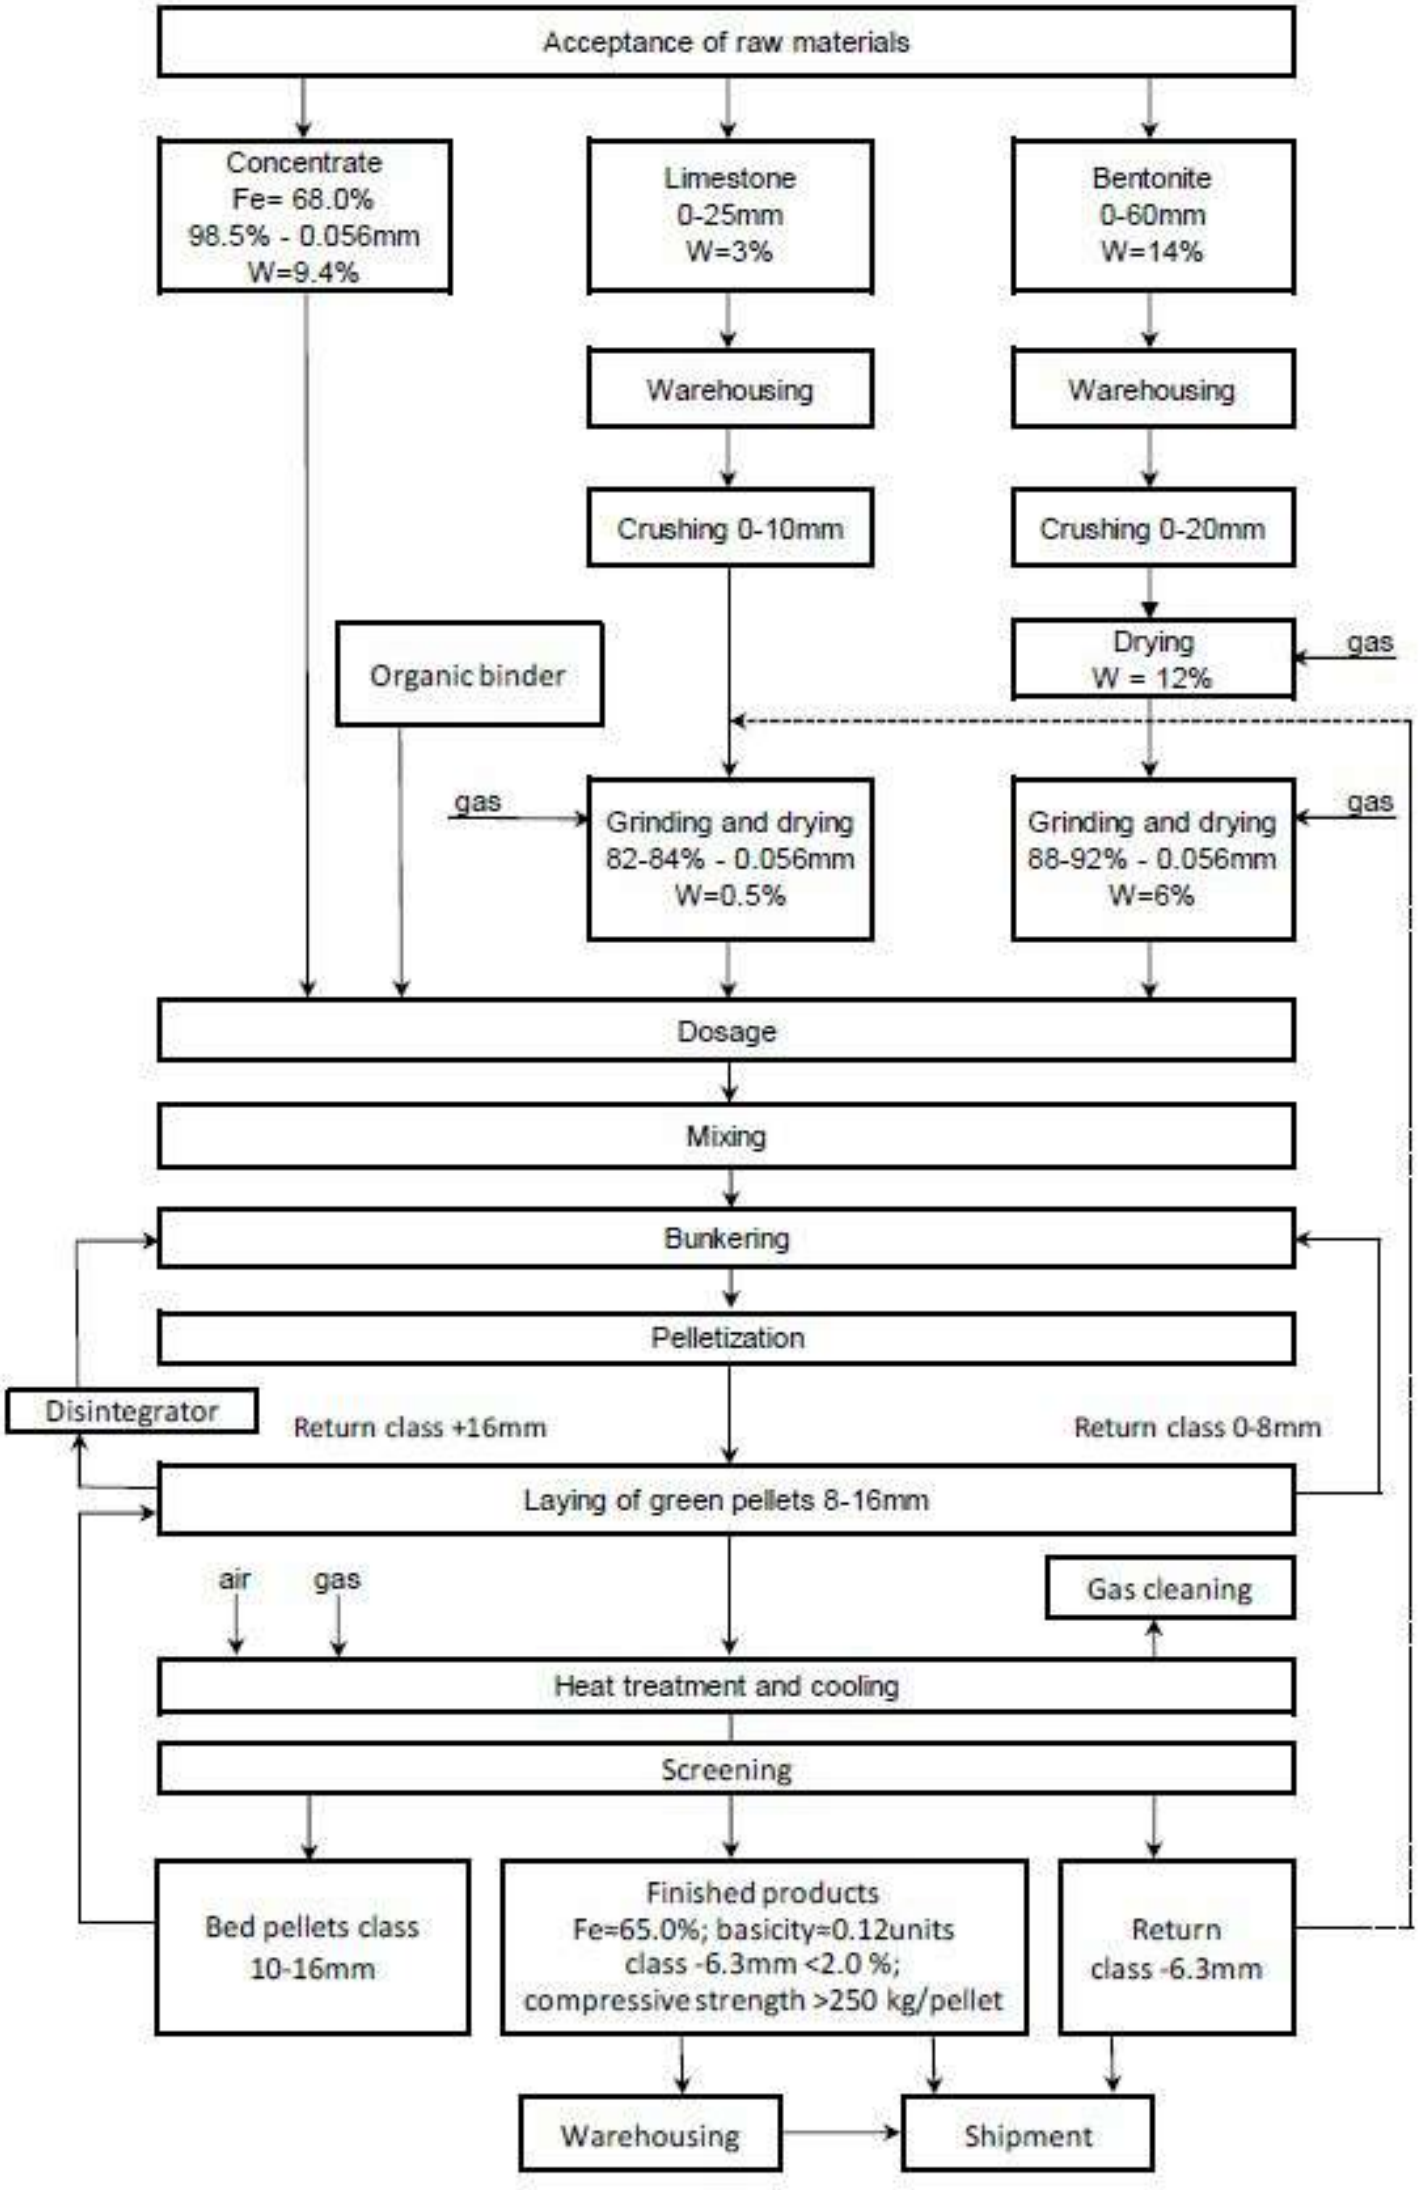

Acceptance of raw materials
Concentrate
Fe= 68.0%
98.5% - 0.056mm
W=9.4%
Limestone
0-25mm
W=3%
Bentonite
0-60mm
W=14%
Warehousing
Warehousing
Crushing 0-10mm
Crushing 0-20mm
Organic binder
Drying
W = 12%
gas
gas
Grinding and drying
82-84% - 0.056mm
W=0.5%
gas
Grinding and drying
88-92% - 0.056mm
W=6%
Dosage
Mixing
Bunkering
Pelletization
Disintegrator
Return class +16mm
Return class 0-8mm
Laying of green pellets 8-16mm
air
gas
Gas cleaning
Heat treatment and cooling
Screening
Bed pellets class
10-16mm
Finished products
Fe=65.0%; basicity=0.12units
class -6.3mm <2.0 %;
compressive strength >250 kg/pellet
Return
class -6.3mm
Warehousing
Shipment